

Recommended Dosage of Sasobit



SASOL

Issue: February 2016


Sasobit is a versatile additive in the field of asphalt road-building. It has been used globally and successfully since 1997. When adding **Sasobit** to bitumen, quality of asphalt mixes improve significantly, even when admixing reclaimed asphalt pavements. The use of **Sasobit** in asphalt mixes is approved and recommended by road authorities in Europe and the world.

Application	Recommended dosage for Sasobit in M. - % by weight of bitumen							Examples
	1,0	1,5	2,0	2,5	3,0	3,5	4,0	
Improved Workability		■						<ul style="list-style-type: none"> • Hard bitumen • Rubber-modified bitumen • Highly polymer-modified bitumen • Difficult to compact asphalt mixes
Temperature Reduction		■						<ul style="list-style-type: none"> • Resource conservation, environmental compliance • Reduction in CO₂ emissions • Reduced wear and tear on machinery • Less bitumen fumes / aerosols • Occupational health and safety • Reduced bitumen ageing
Process Reliability/ Risk Minimization		■						<ul style="list-style-type: none"> • Paving asphalt mixes during poor weather conditions • Thin layers • No compaction failures • Extended period of use • Manual application
Stability				■				<ul style="list-style-type: none"> • Faster reopening to traffic • Optimized asphalt mix design • Improved deformation resistance
Heavy Duty Asphalt Mixes				■				<ul style="list-style-type: none"> • Pavements for industrial premises and logistics centres • Container terminals • Airports • Highly trafficked roads • Bus stops • Race tracks

Keep in mind that softening point ring and ball, the needle penetration, or the bitumen viscosity etc. change according to the quantity of **Sasobit** added or the type of bitumen used. Hence the quantity of **Sasobit** to be added needs to be determined in lab tests.

Working principle: Sasobit's effect on bitumen viscosity

Mixing and paving temperatures can be reduced by as much as 30 K when using **Sasobit**, because above 115 °C **Sasobit** is completely soluble in bitumen and reduces viscosity significantly. Reduced viscosity at standard temperatures enhances the workability of the asphalt mix. **Sasobit** increases process reliability and significantly reduces the risk of improper paving operations. During the cooling phase **Sasobit** starts to crystallize at 90 °C and forms a lattice structure in the bitumen which has a stiffening effect (the frequently cited congealing point of 100 to 105 °C refers to pure **Sasobit**). Deformation resistance increases significantly when adding the appropriate quantity of **Sasobit**, without impairing low-temperature performance.

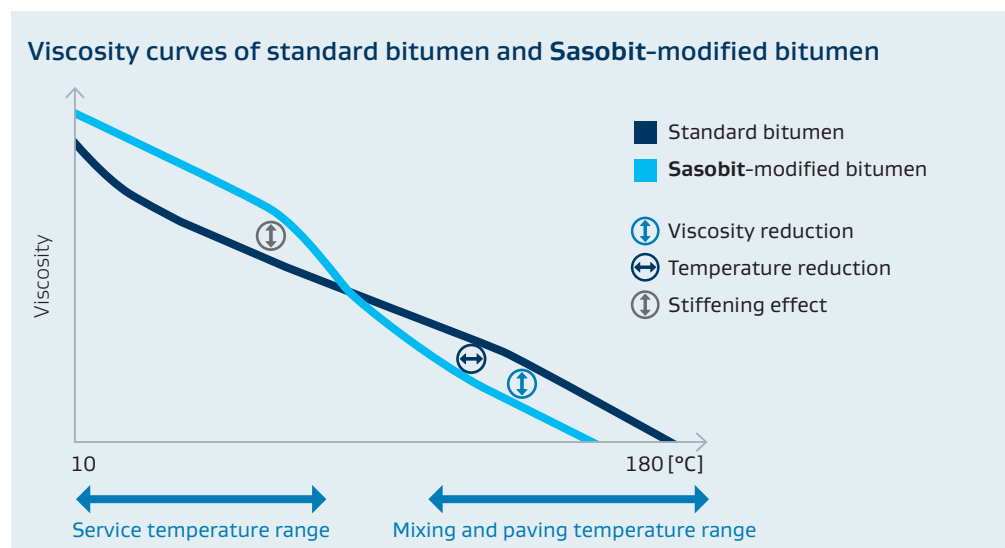

Selected characteristics of bitumen modified with Sasobit

Sasobit modified Bitumen		70/100	SmB 45 70/100+Sasobit ¹	50/70	SmB 35 50/70+Sasobit ¹	30/45	SmB 25 30/45+Sasobit ¹
Penetration at 25 °C	1/10 mm	70 – 100	35 – 55	50 – 70	30 – 50	30 – 45	20 – 35
Softening Point R&B	°C	43 – 49	70 – 80	48 – 54	75 – 85	53 – 59	80 – 90
Frass Breaking Point	°C	≤ -10	≤ -10	≤ -8	≤ -8	≤ -5	≤ -5

Sasobit co-modified PmB		45/80 – 50 A	45/80 – 50 A +Sasobit ¹	25/55 – 55 A	25/55 – 55 A +Sasobit ¹	10/40 – 65 A	10/40 – 65 A +Sasobit ¹
Penetration at 25 °C	1/10 mm	45 – 80	≥ 30	25 – 55	≥ 20	10 – 40	≥ 10
Softening Point R&B	°C	≥ 50	≥ 65	≥ 55	≥ 70	≥ 65	≥ 75
Frass Breaking Point	°C	≤ -15	≤ -15	≤ -10	≤ -10	≤ -5	≤ -5

¹ 2.5 – 3.0 % **Sasobit** by weight as a function of the technical properties of base bitumen

The given values are based on many years of experience. The characteristics after modifying the bitumen with **Sasobit** have to be taken into account when designing the asphalt mix. **Sasobit** is not classified as hazardous substance under currently applicable European law. This means that **Sasobit** can be used without any additional safety precautions.

Sasol Performance Chemicals Wax Division, Asphalt Additives

Worthdamm 13–27, 20457 Hamburg, Deutschland
Tel.: +49 40 78 115-711 sasobit@de.sasol.com

www.sasobit.com



SASOL

This information is based on our present knowledge and experience. However, it implies no liability or other legal responsibility on our part, including any existing third party patent rights. In particular, no guarantee of properties in the legal sense is implied. We reserve the right to make any changes according to technological progress or further developments. The customer is not exempted from the obligation to conduct careful inspection and testing of incoming goods. Reference to trade names used by other companies is neither a recommendation, nor is it intended to suggest that similar products could not be used. All our business transactions shall be governed exclusively by our General Sales Conditions.